

Measuring the proton selectivity of graphene membranes

Michael I. Walker, Philipp Braeuninger-Weimer, Robert S. Weatherup, Stephan Hofmann, and Ulrich F. Keyser

Citation: *Applied Physics Letters* **107**, 213104 (2015); doi: 10.1063/1.4936335

View online: <http://dx.doi.org/10.1063/1.4936335>

View Table of Contents: <http://scitation.aip.org/content/aip/journal/apl/107/21?ver=pdfcov>

Published by the [AIP Publishing](#)

Articles you may be interested in

[Protecting nickel with graphene spin-filtering membranes: A single layer is enough](#)

Appl. Phys. Lett. **107**, 012408 (2015); 10.1063/1.4923401

[Free-standing graphene membranes on glass nanopores for ionic current measurements](#)

Appl. Phys. Lett. **106**, 023119 (2015); 10.1063/1.4906236

[Strain and morphology of graphene membranes on responsive microhydrogel patterns](#)

Appl. Phys. Lett. **105**, 193103 (2014); 10.1063/1.4901746

[Enhanced sensitivity of a microfabricated resonator using a graphene-polystyrene bilayer membrane](#)

Appl. Phys. Lett. **105**, 073116 (2014); 10.1063/1.4893741

[MnO₂ nanotube-Pt/graphene mixture as an ORR catalyst for proton exchange membrane fuel cell](#)

AIP Conf. Proc. **1512**, 370 (2013); 10.1063/1.4791065

The advertisement for MMR Technologies features a blue and white background with a grid pattern. On the left is the MMR Technologies logo, which consists of a stylized 'M' and 'R' in a blue and red arc, with 'TECHNOLOGIES' written below. To the right of the logo is the text 'THE WORLD'S RESOURCE FOR VARIABLE TEMPERATURE SOLID STATE CHARACTERIZATION' in bold, black, uppercase letters. Below this text are five images of different scientific instruments: 1. Optical Studies Systems (a small white device), 2. Seebeck Studies Systems (a blue device labeled SB1000 and K2000), 3. Microprobe Stations (a circular device with multiple ports), 4. Hall Effect Study Systems and Magnets (a blue device labeled H5000 and K2000), and 5. A large cylindrical magnet. At the bottom left of the advertisement is the website address 'WWW.MMR-TECH.COM' in red text. Below each of the five images is a label: 'OPTICAL STUDIES SYSTEMS', 'SEEBECK STUDIES SYSTEMS', 'MICROPROBE STATIONS', and 'HALL EFFECT STUDY SYSTEMS AND MAGNETS'.

Measuring the proton selectivity of graphene membranes

Michael I. Walker,¹ Philipp Braeuninger-Weimer,² Robert S. Weatherup,² Stephan Hofmann,² and Ulrich F. Keyser^{1,a)}

¹*Cavendish Laboratory, University of Cambridge, J.J. Thomson Avenue, Cambridge CB3 0HE, United Kingdom*

²*Department of Engineering, University of Cambridge, Cambridge CB3 0FA, United Kingdom*

(Received 18 August 2015; accepted 11 November 2015; published online 25 November 2015)

By systematically studying the proton selectivity of free-standing graphene membranes in aqueous solutions, we demonstrate that protons are transported by passing through defects. We study the current-voltage characteristics of single-layer graphene grown by chemical vapour deposition (CVD) when a concentration gradient of HCl exists across it. Our measurements can unambiguously determine that H^+ ions are responsible for the selective part of the ionic current. By comparing the observed reversal potentials with positive and negative controls, we demonstrate that the as-grown graphene is only weakly selective for protons. We use atomic layer deposition to block most of the defects in our CVD graphene. Our results show that a reduction in defect size decreases the ionic current but increases proton selectivity. © 2015 AIP Publishing LLC.

[<http://dx.doi.org/10.1063/1.4936335>]

The selective transport of ions across graphene membranes in aqueous solutions is a key issue for high profile applications such as water desalination and proton exchange membranes. A number of studies have reported simulations,^{1,2} measurements of filtration through graphene membranes,^{3–6} and the translocations of macromolecules.^{7–9} Proton transport across graphene membranes is especially interesting as recent reports have suggested proton selective transport across intact graphene membranes.¹⁰ However, there is little consensus regarding the mechanisms of transport and the appropriate experiments to conclude that a graphene membrane is proton selective.

Determining which ions cross a membrane is a problem that has been extensively studied in the field of ion channels. Selective transport of ions and macromolecules across biological membranes is critical to the operation of biological systems. Since the work of Hodgkin and Huxley in 1939, these have traditionally been investigated by electrophysiology techniques and single channel measurements.¹¹ These methods can be used to determine selective transport in the presence of leakage and multiple transport pathways.

An established and immediate measurement of ion selectivity is to set up a concentration gradient over the membrane as shown in Fig. 1(a). This creates a driving force for diffusion for both the positive and negative ions. However, if one of the ions can pass through the membrane more easily than the other, then there will be a measurable net current flow across the membrane when the potential is zero, indicated by point B in the idealised current (I) - voltage (V) characteristic in Fig. 1(b).¹² This current can be stopped by applying an opposing electric field. The corresponding voltage is called the reversal potential and is illustrated as point A in Fig. 1(b). The voltage required is predicted by the Nernst equation, but deviations from the expected value can be used to assess the importance of leakage currents.¹²

Here, we present experiments to study the selectivity of graphene membranes to protons in aqueous solutions. By systematically measuring the competition between H^+ and Cl^- ions to cross single layer graphene membranes, we can distinguish which ion is carrying the current. This is critical because all measurements across a membrane will measure a leakage current. This current could be passing via the seal around the membrane, directly through the substrate or, importantly for graphene, could be due to the defects in the sample. To dissociate the selective effect from a leakage current, we create a concentration difference and investigate the I-V characteristics. From the reversal potential, we can determine the extent to which our chemical vapour deposition (CVD) graphene membranes are selective to protons. To establish the effect of defects, we block the pores using atomic layer deposition (ALD) and as a positive control present results using the proton selective membrane Nafion.

We seal graphene membranes on to the tips of pulled glass nanocapillaries with diameters of $d = 180$ nm and $d = 2$ μ m using the method developed in Ref. 13 and illustrated in Fig. 1(a). The graphene adheres to the tips of the

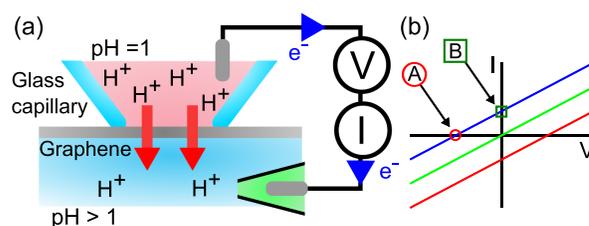


FIG. 1. (a) A schematic of our experiment showing a glass nanocapillary sealed with a graphene membrane separating HCl solutions of different concentrations. Ag/AgCl electrodes in the reservoir and the capillary connect the experiment to an amplifier which applies a voltage and measures the current. The arrows show the diffusion current of protons due to the concentration gradient. (b) An illustration of the expected changes in the I-V characteristic when a concentration gradient across a selective membrane drives a diffusion current at zero potential (B) and the reversal potential required to stop the current (A).

^{a)}ufk20@cam.ac.uk

capillaries so that the solution in the reservoir can be exchanged for a different concentration. Ag/AgCl electrodes in the capillary and reservoir carry the current which is measured using an Axopatch 200B amplifier (*Molecular Devices*) used to take I-V curve measurements. Graphene was grown by chemical vapour deposition in an Aixtron BM Pro (4 in.) reactor, using $25\ \mu\text{m}$ thick Cu foil (Alfa Aesar, 99.8%) as the catalyst and CH_4 (diluted in Ar and H_2) as the precursor at $1050\ ^\circ\text{C}$.¹⁴ Our single-layer graphene significantly impedes the flow of current.¹³ We keep the solution inside the capillaries at 0.1M HCl and vary the concentration of the HCl solution in the reservoir. It is important to ensure the electrode potentials remain constant, despite changing the concentration of the reservoir. To achieve this, we use agarose coated electrodes made up in 0.1M KCl solution (Fig. 1(a)). Our negative control experiments, using bare capillaries, show that the solution can be exchanged without a significant current being induced when no membrane is present. As a positive control we will present results using the proton selective membrane Nafion;¹⁵ a commercial proton exchange membrane. It is highly conductive to protons (cations) but blocks anions. The Nafion is $100\ \mu\text{m}$ thick and is contacted in the same way as the graphene.

Typical I-V curves for each material are shown in Fig. 2. The I-V curves for a bare capillary show voltage offsets of less than 5 mV which correspond to a small component of the current being selective due to the negative charge on the surface of the glass nanocapillaries. A fully selective

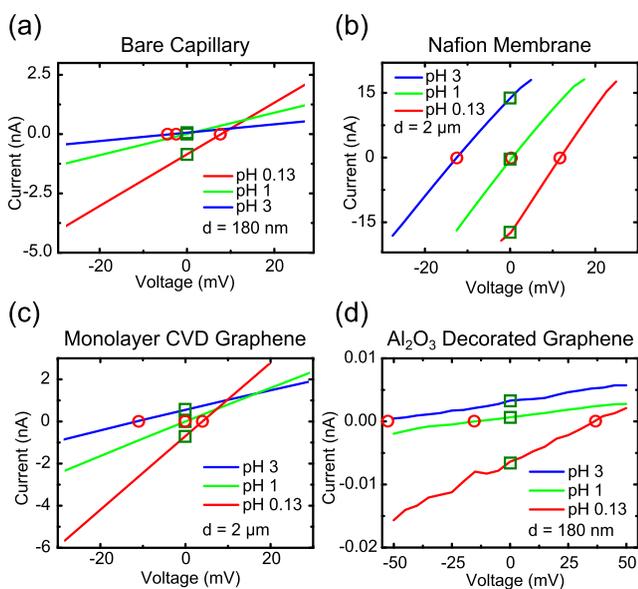


FIG. 2. Typical I-V curves for different concentration differences. The concentration in the capillary is 0.1 M HCl and the HCl solution in the reservoir is indicated in the legends. The red circles indicate the reversal potential (“A”) and the green squares indicate the diffusion driven current (“B”). We use capillaries with diameter $d = 180\ \text{nm}$ and $d = 2\ \mu\text{m}$ as indicated in the figure. (a) For a bare capillary (diameter $d = 180\ \text{nm}$), the lines pass close to 0,0 indicating minimal selectivity associated with the charge on the glass. (b) The commercially available proton selective membrane Nafion (diameter $d = 2\ \mu\text{m}$). When there is a concentration difference across the capillary, the current flows at 0 V. This current can be stopped by applying the reversal potential. (c) Typical I-V curves for an as grown monolayer graphene membrane, small voltage offsets indicate that there is weak evidence for selectivity (diameter $d = 2\ \mu\text{m}$). (d) Typical I-V curves for a graphene membrane decorated with Al_2O_3 (diameter $d = 180\ \text{nm}$). Here the voltage offsets are similar to those for Nafion.

membrane would cause a reversal potential of 58 mV per unit pH difference, so this indicates that less than 10% of the current is selective. Most of the current flows through the centre of the capillary and is carried equally by the positive and negative ions. In contrast, the Nafion membrane measurements show a clear shift in the voltage and current as the concentration of HCl in the reservoir changes (Fig. 2(b)). Offsets of 15 to 20 mV clearly indicate that a significant proportion of the current is due to protons. However, as the reversal potential does not shift by 58 mV it is clear that there is also a significant leakage current. These results confirm that our experiment can detect and quantify selectivity in the presence of other ionic currents.

The I-V curves for an as grown graphene membrane show evidence for limited selectivity, Fig. 2(c). The voltage offsets are of the order of 5–10 mV which indicates that a small proportion of the current is proton selective. However, we find that the leakage currents dominate over any selective current for our CVD graphene membranes.

Given that defects in the CVD graphene are known to influence ionic flow, it is necessary to establish the extent to which the defects affect the current. We therefore used an ALD process to block most of the defects. Al_2O_3 is deposited onto the NaCl supported graphene using a Cambridge Nanotech Savannah ALD system with a 20 cycle process at $200\ ^\circ\text{C}$, consisting of alternating pulses of trimethylaluminium and water both carried in a N_2 (20 sccm) flow with 8 s purges between them.^{16,17} This method typically yields a 2 nm thick film on Si with a native oxide. However, for this relatively high-temperature, water-based process, the poor wetting of the Al_2O_3 on graphene, is well documented, leading to preferential decoration at defects.^{16,18–20} It has been demonstrated that Al_2O_3 deposited by ALD reduces the ionic current²¹ and our samples indeed showed significantly increased resistance (shown in the supplementary material²²). Typical I-V curves for Al_2O_3 decorated graphene are shown in Fig. 2(d). The shape of these I-V curves more closely resembles those observed for Nafion than for either bare capillaries or as grown graphene. We measure reversal potentials of 15–25 mV, indicating that a significant proportion of the current is due to a proton flux, although the overall currents are the lowest of the three.

We can further quantify the selectivity of the membranes by analysing the reversal potentials (point A in Fig. 1(a)). These are plotted in Figs. 3(a)–3(c) against the difference in pH of the solutions in the capillary and reservoir. From Fig. 3, we observe that none of the fitted lines have a gradient of 58 mV/pH indicating that there is always a leakage current. The bare capillaries show evidence of very low selectivity with a gradient of 2 mV/pH, whereas the Nafion is ten times more selective with a gradient of 20 mV/pH (Fig. 3(a)). As grown graphene has a gradient of 8 mV/pH, though the error bars are significant (Fig. 3(b)). This means that whilst there is some selectivity, the bulk of current flow is due to non-selective leakage current. We do not observe a significant difference in selectivity between the results from $2\ \mu\text{m}$ and 180 nm capillaries. However, the graphene decorated with Al_2O_3 has a gradient of 23 mV/pH (Fig. 3(c)) and exhibits proton selectivity comparable to Nafion.

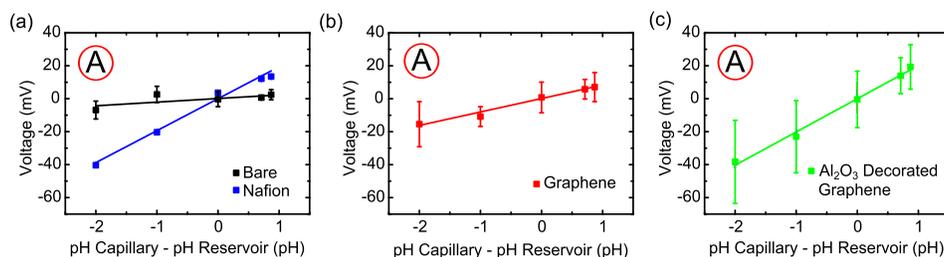


FIG. 3. The voltage offsets plotted against the difference in capillary and reservoir pH for each of the four conditions (this corresponds to point “A” in Fig. 1(b)). (a) The bare capillaries show a gradient of 2.2 mV/pH indicating the effect of negative charge on the surfaces of the glass nanocapillaries. The Nafion shows a 19.4 mV/pH offset indicating that the membrane is selective. (b) As grown graphene has a voltage offset of 8.1 mV/pH. (c) Al₂O₃ decorated graphene shows an offset comparable with Nafion of 23 mV/pH indicating significant selectivity.

TABLE I. Table of average selectivity in mV/pH and the average conductivities of different samples broken down into leakage and selective current.

Membrane	Selectivity (mV/pH)	Conductivity nA/ μm^2	Leakage conductivity nA/ μm^2	Selective H ⁺ conductivity nA/ μm^2
Bare glass nanopore	2.2 ± 0.56	800	740	60
Nafion	19.4 ± 0.78	18.7	12.5	6.2
As grown CVD graphene	8.1 ± 0.70	16.4	15.1	1.3
Al ₂ O ₃ decorated graphene	23 ± 1.6	1.2	0.8	0.4

The leakage conductivity for each membrane can be calculated from the ratio of the observed voltage per pH to the expected voltage per pH and the measured conductivity.²³ The leakage and selective pathways form a voltage divider relating the measured membrane voltage V_m , with the measured membrane conductance G_m , and the leakage conductance G_0 , to the Nernstian potential V (Ref. 23)

$$V_m = V \frac{G_m - G_0}{G_m}. \quad (1)$$

Using Eq. (1), we can estimate the selective proton conductivity for the as grown and Al₂O₃ decorated graphene, shown in Table I.

To consider where this selectivity arises from, it is instructive to consider the current density at zero potential

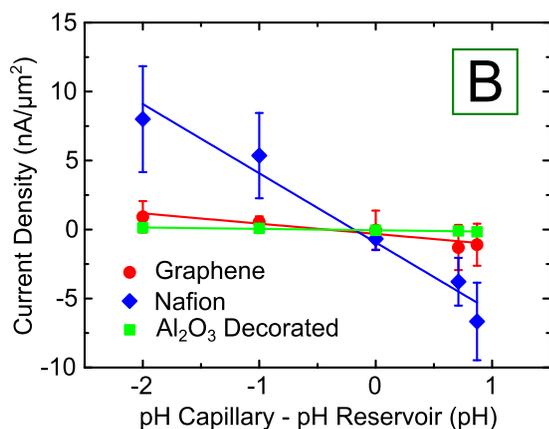


FIG. 4. The current density at zero voltage plotted against the difference in capillary and reservoir pH, for capillaries with diameter $d = 180$ nm and $d = 2$ μm (this corresponds to point “B” in Fig. 1(b)). This plot shows the concentration difference driven current when the amplifier in voltage track mode holds the voltage at 0 V. All the samples show the current decreasing with increased pH in the reservoir as expected for selectivity. However, the Nafion currents are much higher than those for graphene membranes. The lowest currents are across the Al₂O₃ sample. These results are presented separately in the supplementary material.²²

(point B in Fig. 1(b)) plotted in Fig. 4. For a selective membrane, the concentration gradient will drive a current when the potential is zero. We see that both the as grown and decorated graphene show a current that scales with pH. However, for the Al₂O₃ decorated graphene it is much lower. We interpret this as current flowing through the defects in as grown graphene. Adding Al₂O₃ blocks the defects decreasing *both* the selective and nonselective components of current. This can also be seen in the values of the conductivities in Table I. The proton conductivity for as grown graphene is 1.3 nA/ μm^2 compared to 0.4 nA/ μm^2 for Al₂O₃ decorated graphene, despite the latter being three times more selective to protons.

We propose that the increase in selectivity is due to the defects decreasing in size and hence becoming more size selective for H⁺ over Cl⁻. Blocking the defects decreases both the selective and nonselective components of the conductivity through the graphene. This shows that the small amount of selectivity observed for the bare graphene

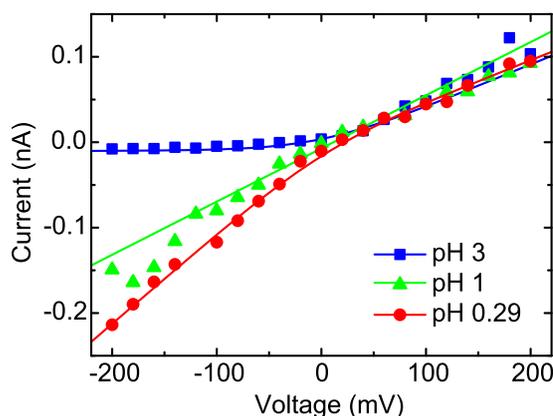


FIG. 5. Plots of I-V curves for an Al₂O₃ decorated graphene membrane sealed across a 180 nm capillary. The capillary contains 0.1 M HCl and the concentration in the reservoir is exchanged. The lines show the fitted GHK equation, from which the permeability coefficients can be determined.

membrane can also be attributed to selective defects. If the protons passed directly through the membrane as opposed to defects, then we would not expect the proton current to decrease significantly when the defects are blocked. In contrast to a recently published result,¹⁰ this indicates that proton transport across the graphene membranes is via defects supporting the results in Ref. 24 which comes to a similar conclusion for graphene supported on a substrate.

An alternative analysis of our I-V characteristics can also be made by considering the Goldman Hodgkin Katz (GHK) equations.²⁵ These predict the shape of the I-V curve expected for a selective membrane.¹² See the supplementary material for further details.²² We only observed results which correspond to the GHK equations for the Al₂O₃ decorated graphene membrane (Fig. 5). When the capillary is at a higher concentration than the reservoir, positive currents are larger indicating that protons can cross from the capillary into the reservoir. However when a negative voltage is applied the current is decreased since there are fewer protons in the reservoir to cross into the capillary, demonstrating that the Cl⁻ ions in excess in the capillary are unable to cross the membrane and contribute to the current (blue line in Fig. 5). When the concentration gradient is reversed, the relative currents switch around so that the current due to a negative applied voltage is higher than the current for a positive applied voltage (red line Fig. 5). The ratio between the permeability of the positive and negative ions indicates proton selectivity. When the reservoir is at pH 0.29, we measure a ratio of 3.5 which would correspond to a reversal potential of 20 mV, consistent with the reversal potentials we have observed.

The high relative selectivity of the Al₂O₃ decorated graphene suggests it could be utilised as a selective membrane, for example, in fuel cells. However, on the basis of our results, we think there are significant challenges as the proton fluxes observed are much lower than for Nafion. The graphene membranes are either less selective or less permeable to protons than their commercial competitors.

Our results show that defects are critical for ionic transport and selectivity in our graphene membranes. Understanding the nature of these defects and how their size and chemistry influences their selectivity is a key challenge. We have shown that even a very small number of defects or partially blocked defects can dominate ionic transport properties. Verifying that no defects exist in a graphene membrane is extremely challenging. The minimum defect density detectable in Raman spectroscopy is about $2 \times 10^9 \text{ cm}^{-2}$ hence up to 20 defects may exist per $1 \mu\text{m}^2$ of graphene where Raman spectroscopy indicates defect free graphene.^{26–28} Conversely, TEM or STM has sufficient resolution to locally image individual defects but it is not practical to image the entirety of the graphene covering a $2 \mu\text{m}$ pore.

We have measured the selectivity of Nafion and graphene membranes to H⁺ by analysing the I-V characteristics when there is a concentration difference across the membrane. Our results show that a leakage current does not prevent the use of established techniques to probe selectivity in aqueous solutions. By studying reversal potentials, we have identified a small proton selective current through graphene membranes which can be reduced by blocking defects.

We conclude that the proton selective current is through defects as opposed to across the graphene membrane.

The authors would like to thank C. Chimereel for useful discussions. This work was supported by the EPSRC Cambridge NanoDTC, EP/G037221/1, and EPSRC Grant GRAPHTED, EP/K016636/1. R.S.W. acknowledges a Research Fellowship from St. John's College, Cambridge and a Marie Skłodowska-Curie Individual Fellowship (Global) under grant ARTIST (no. 656870) from the European Union's Horizon 2020 research and innovation programme. All data accompanying this publication are directly available within the publication.

- ¹K. Sint, B. Wang, P. Král, and P. Kra, *J. Am. Chem. Soc.* **130**, 16448 (2008).
- ²Y. Kang, Z. Zhang, H. Shi, J. Zhang, L. Liang, Q. Wang, H. Agren, and Y. Tu, *Nanoscale* **6**, 10666 (2014).
- ³S. P. Surwade, S. N. Smirnov, I. V. Vlassioug, R. R. Unocic, G. M. Veith, S. Dai, and S. M. Mahurin, *Nat. Nanotechnol.* **10**, 459 (2015).
- ⁴S. C. O'Hern, C. A. Stewart, M. S. H. Boutilier, J.-C. Idrobo, S. Bhaviripudi, S. K. Das, J. Kong, T. Laoui, M. Atieh, and R. Karnik, *ACS Nano* **6**, 10130 (2012).
- ⁵S. C. O'Hern, M. S. H. Boutilier, J.-C. C. Idrobo, Y. Song, J. Kong, T. Laoui, M. Atieh, and R. Karnik, *Nano Lett.* **14**, 1234 (2014).
- ⁶S. P. Koenig, L. Wang, J. Pellegrino, and J. S. Bunch, *Nat. Nanotechnol.* **7**, 728 (2012).
- ⁷S. Garaj, W. Hubbard, A. Reina, J. Kong, D. Branton, and J. A. Golovchenko, *Nature* **467**, 190 (2010).
- ⁸G. F. Schneider, S. W. Kowalczyk, V. E. Calado, G. Pandraud, H. W. Zandbergen, L. M. K. Vandersypen, and C. Dekker, *Nano Lett.* **10**, 3163 (2010).
- ⁹C. A. Merchant, K. Healy, M. Wanunu, V. Ray, N. Peterman, J. Bartel, M. D. Fischbein, K. Venta, Z. Luo, A. T. C. Johnson, and M. Drndić, *Nano Lett.* **10**, 2915 (2010).
- ¹⁰S. Hu, M. Lozada-Hidalgo, F. C. Wang, A. Mishchenko, F. Schedin, R. R. Nair, E. W. Hill, D. W. Boukhvalov, M. I. Katsnelson, R. A. W. Dryfe, I. V. Grigorieva, H. A. Wu, and A. K. Geim, *Nature* **516**, 227 (2014).
- ¹¹A. L. Hodgkin and A. F. Huxley, *Nature* **144**, 710 (1939).
- ¹²B. Hille, *Ion Channels of Excitable Membranes*, 3rd ed. (Sinauer Associates, 2001), pp. 441–470.
- ¹³M. I. Walker, R. S. Weatherup, N. A. W. Bell, S. Hofmann, and U. F. Keyser, *Appl. Phys. Lett.* **106**, 023119 (2015).
- ¹⁴S. Hofmann, P. Braeuninger-Weimer, and R. S. Weatherup, *J. Phys. Chem. Lett.* **6**, 2714 (2015).
- ¹⁵K. A. Mauritz and R. B. Moore, *Chem. Rev.* **104**, 4535 (2004).
- ¹⁶B. Dlubak, P. R. Kidambi, R. S. Weatherup, S. Hofmann, and J. Robertson, *Appl. Phys. Lett.* **100**, 173113 (2012).
- ¹⁷R. S. Weatherup, C. Baecht, B. Dlubak, B. C. Bayer, P. R. Kidambi, R. Blume, R. Schloegl, and S. Hofmann, *Nano Lett.* **13**, 4624 (2013).
- ¹⁸X. Wang, S. Tabakman, and H. Dai, *J. Am. Chem. Soc.* **130**, 8152 (2008).
- ¹⁹J. A. Robinson, M. Labella, K. A. Trumbull, X. Weng, R. Cavellero, T. Daniels, Z. Hughes, M. Hollander, M. Fanton, and D. Snyder, *ACS Nano* **4**, 2667 (2010).
- ²⁰M. B. Martin, B. Dlubak, R. S. Weatherup, H. Yang, C. Deranlot, K. Bouzehouane, F. Petroff, A. Anane, S. Hofmann, J. Robertson, A. Fert, and P. Seneor, *ACS Nano* **8**, 7890 (2014).
- ²¹S. C. O'Hern, D. Jang, S. Bose, J.-C. Idrobo, Y. Song, T. Laoui, J. Kong, and R. Karnik, *Nano Lett.* **15**, 3254 (2015).
- ²²See supplementary material at <http://dx.doi.org/10.1063/1.4936335> for examples of the graphene seals, detail of the current offsets and further information on the GHK equations.
- ²³C. Chimereel, A. J. Murray, E. R. Oldewurtel, D. K. Summers, and U. F. Keyser, *ChemPhysChem* **14**, 417 (2013).
- ²⁴J. L. Achtyl, R. R. Unocic, L. Xu, Y. Cai, M. Raju, W. Zhang, R. L. Sacci, I. V. Vlassioug, P. F. Fulvio, P. Ganesh, D. J. Wesolowski, S. Dai, A. C. T. van Duin, M. Neurock, and F. M. Geiger, *Nat. Commun.* **6**, 6539 (2015).
- ²⁵D. E. Goldman, *J. General Physiol.* **27**, 37 (1943).
- ²⁶L. G. Cançado, A. Jorio, E. H. M. Ferreira, F. Stavale, C. A. Achete, R. B. Capaz, M. V. O. Moutinho, A. Lombardo, T. S. Kulmala, and A. C. Ferrari, *Nano Lett.* **11**, 3190 (2011).
- ²⁷A. C. Ferrari and D. M. Basko, *Nat. Nanotechnol.* **8**, 235 (2013).
- ²⁸M. Lucchese, F. Stavale, E. M. Ferreira, C. Vilani, M. Moutinho, R. B. Capaz, C. Achete, and A. Jorio, *Carbon* **48**, 1592 (2010).